

On the occurrence of Berezinskii-Kosterlitz-Thouless behavior in highly anisotropic cuprate superconductors

T. Schneider

Physikinstitut, University of Zurich, Winterthurerstrasse 190, 8057 Zurich, Switzerland.

(Dated: February 6, 2008)

The conflicting observations in the highly anisotropic $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$, evidence for BKT behavior emerging from magnetization data and smeared 3D-xy behavior, stemming from the temperature dependence of the magnetic in-plane penetration depth are traced back to the rather small ratio, $\xi_c^+/\xi_c^- = \xi_{c0}^+/\xi_{c0}^- \simeq 0.45$, between the c -axis correlation length probed above (ξ_c^+) and below (ξ_c^-) T_c and the comparatively large anisotropy. The latter leads to critical amplitudes $\xi_{c0}^\pm$ which are substantially smaller than the distance between two CuO_2 double layers. In combination with $\xi_c^+/\xi_c^- \simeq 0.45$ and in contrast to the situation below T_c the c -axis correlation length ξ_c^+ exceeds the distance between two CuO_2 double layers very close to T_c only. Below this narrow temperature regime where 3D-xy fluctuations dominate, there is then an extended temperature regime where the units with two CuO_2 double layers are nearly uncoupled so that 2D thermal fluctuations dominate and BKT features are observable.

PACS numbers: 74.72.-h, 74.25.Ha, 64.60.Fr

Since the pioneering work of Berezinskii[1], Kosterlitz and Thouless[2] (BKT) on the BKT transition in the two-dimensional (2D) XY model, much efforts have been devoted to observe the universal behavior characteristic of the KT transition, as the universal jump of the superfluid density[3], measured in ^4He superfluid films, or the non-linear I - V characteristic, observed in thin films of conventional superconductors[4, 5]. Signatures of BKT physics can be expected also in layered superconductors with weak inter-layer coupling. Potential candidates are underdoped cuprate superconductors where the anisotropy increases with reduced transition temperature T_c [6]. Recent studies of the I-V characteristic[7], the frequency dependent conductivity[8], the Nernst signal[9], the magnetization[10, 11], and of the resistance[12] have been interpreted as signatures of BKT behavior. On the other hand, several experiments [13, 14, 15, 16, 17, 18, 19, 20, 21] failed to observe any trace of the universal jump in the superfluid density around T_c . Indeed, a systematic finite-size scaling analysis of in-plane penetration depth data taken on films and single crystals of the highly anisotropic $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ reveal a smeared transition, consistent with an inhomogeneity induced finite-size effect[22]. Furthermore, there is evidence that in small thin-film samples on insulating substrates, edge effects modify the vortex-vortex interaction making it short-range, unlike the logarithmic long-range interaction needed for the BKT transition. This appears to make the BKT transition impossible in thin films of any size if they are supported by a non-superconducting substrate[23].

In this work we attempt to unravel the conflicting observations on the highly anisotropic $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$: evidence for BKT behavior emerging from the magnetization data of Li *et al.* [10] and evidence for smeared 3D-xy behavior, stemming from the temperature dependence of the magnetic in-plane penetration depth [13, 16, 22]. Al-

though $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ is highly anisotropic [24], resistivity measurements [25] uncover clearly the three dimensional nature of the transition in this extreme type II superconductor. Accordingly, sufficiently close to T_c homogeneous samples are expected to exhibit 3D-xy critical behavior. To explore how close this should be, we consider the magnetic in-plane penetration data shown in Fig. 1, derived from the complex conductivity measurements of Osborn *et al.* [16] on epitaxially grown $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ films, using a two-coil inductive technique at zero applied field. For comparison we included the leading 3D-xy behavior given by the universal relation [5, 22, 26, 27]

$$\frac{1}{\lambda_{ab}^2(T)} = \frac{16\pi^3 k_B T}{\Phi_0^2 \xi_c^-(T)}, \quad \xi_c^- = \xi_{c0}^- |t|^{-\nu}, \quad (1)$$

with

$$t = T/T_c - 1, \quad \nu \simeq 2/3. \quad (2)$$

Apparently, there is a rounded transition pointing to a finite size effect, preventing the c -axis correlation length ξ_c^- to grow beyond the limiting length L_c , set by inhomogeneities. Indeed the extreme in $d\text{Re}(\rho)/dT$ exhibits an inflection point at $T = T_{pc} \simeq 83.77$ K where ξ_c^- attains the limiting length L_c . As shown previously [22], Eq. (1) yields together with $T_c = 84$ K, $T_{pc} \simeq 83.77$ K, $\text{Re}(\rho(T_c))/\text{Re}(\rho(T=0)) = 0.011$, $\text{Re}(\rho(T=0)) = 0.6$ K, $\text{Re}(\rho(T_{pc})) = 13.66$ K, $\lambda_{ab}(0) = 265$ nm, and $L_c = \xi_c^-(T_{pc})$ the estimates

$$\xi_{c0}^- \simeq 2\text{\AA}, \quad L_c \simeq 93\text{\AA}, \quad (3)$$

for the critical amplitude of the c -axis correlation length below T_c and the limiting length L_c set by inhomogeneities. The rather small value of ξ_{c0}^- , reflecting the

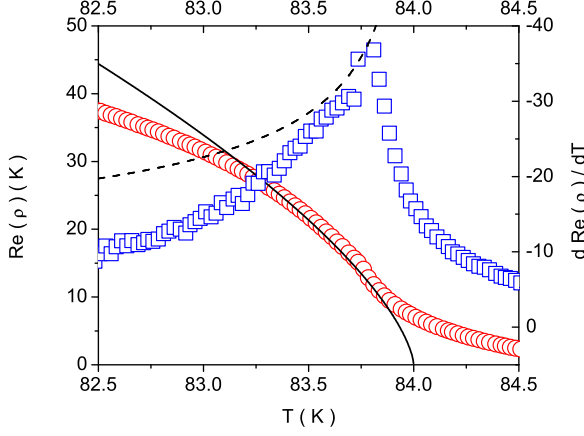


FIG. 1: $\text{Re}(\rho) \propto 1/\lambda_{ab}^2$ and $d\text{Re}(\rho)/dT$ vs. T for the $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ film B, 616 Å thick, derived from Osborn *et al.*[16]. The solid and dashed lines indicate the leading critical behavior of a homogeneous bulk system according to Eq. 1, where $\text{Re}(\rho) = 650 |t|^{2/3}$ with $T_c = 84$ K.

high anisotropy, $\gamma = \xi_{ab0}^-/\xi_{c0}^-$, was confirmed in other $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ films and single crystals in terms of a detailed finite size scaling analysis [22].

Although the c -axis correlation length ξ_c^- increases by approaching T_c , the occurrence of 3D thermal fluctuations requires that in $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ it exceeds $s = 15$ Å, the distance between two CuO_2 double layers. In Fig. 2 we depicted the temperature dependence of ξ_c^- . Even though it exceeds 15 Å around 80 K, a glance to Fig. 1 shows that consistency with 3D-xy behavior is achieved much closer to T_c only, namely above $T \approx 83.25$ K. Accordingly, the occurrence of 3D-xy behavior requires ξ_c^- to exceed the distance between two CuO_2 double layers by at least a factor of three. Above T_c the situation is even worse because the ratio between the correlation lengths above (ξ_c^+) and below (ξ_c^-) T_c is a universal quantity and in the 3D-xy universality class given by

$$\xi_{c0}^+/\xi_{c0}^- \simeq 0.45. \quad (4)$$

This ratio implies a substantial shrinkage of the 3D-xy fluctuation dominated regime above T_c . To illustrate this point we included in Fig. 2 the temperature dependence of ξ_c^+ . Taking again $\xi_c^+ \gtrsim 3s = 45$ Å to locate the regime where 3D-xy fluctuations dominate we obtain roughly $T \gtrsim 83.8$ K which is rather close to the $T_c \simeq 84$ K of the fictitious homogeneous system.

Given the reduced 3D-xy critical regime above T_c the system corresponds to a stack of nearly independent units with two CuO_2 double layers as long as $\xi_c^+ \lesssim 3s$. In this intermediate regime, 2D and in particular BKT features are then expected. To check this expectation quantitatively we consider the 3D-xy scaling expression for the susceptibility in the limit $T \gtrsim T_c$ and $H_c \rightarrow 0$

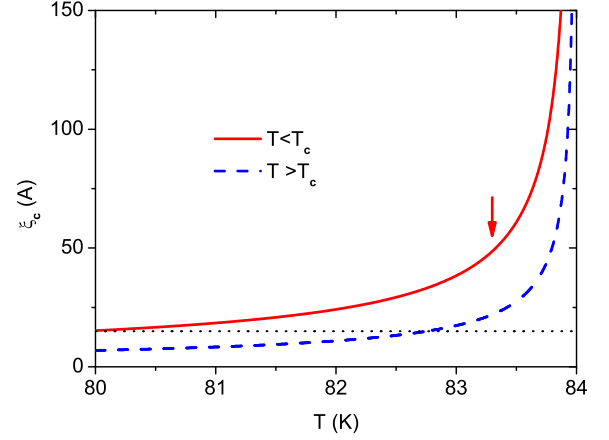


FIG. 2: ξ_c^- and ξ_c^+ vs. T for $\xi_{c0}^- = 2$ Å, $\xi_{c0}^+ = 0.9$ Å and $T_c = 84$ K, where $\xi_c^\pm = \xi_{c0}^\pm |t|^{-2/3}$. The dotted line marks $s = 15$ Å, the distance between two CuO_2 double layers. The arrow marks $T = 83.25$ K where in Fig. 1 consistency with 3D-xy critical behavior sets in.

[5, 28, 29, 30]

$$\frac{m}{H_c} = -\frac{Q^+ C_{3,0}^+ k_B T (\xi_{ab}^+)^2}{\Phi_0^2 \xi_c^+}, \quad (5)$$

where $m = M/V$ is the magnetization per unit volume and $Q^+ C_{3,0}^+ \simeq 0.9$ a universal number. In type II superconductors, exposed to a magnetic field H_i in direction i , there is also the magnetic field induced limiting length $L_{H_i} = \sqrt{\Phi_0/(aH_i)}$ with $a \simeq 3.12$ [31], related to the average distance between vortex lines [26, 31]. As the magnetic field increases, the density of vortex lines becomes greater, but this cannot continue indefinitely, the limit is roughly set on the proximity of vortex lines by the overlapping of their cores. Due to these limiting length the phase transition is rounded and occurs smoothly. Indeed, approaching T_c from above the correlation lengths combination $\xi_i^+ \xi_j^+$ increases but is bounded by $L_{H_k}^2 = \Phi_0/(aH_k)$ where $i \neq j \neq k$. In this context it is important to recognize that the confinement effect of the magnetic field in direction i on fluctuations within a region L_{H_i} acts only in the plane perpendicular to the field. Therewith Eq. (5) reduces for $T \simeq T_c$ and $H_c \rightarrow 0$ to

$$\frac{m}{H_c} = -\frac{Q^+ C_{3,0}^+ k_B T \gamma}{\Phi_0^{3/2} a^{1/2} H_c^{1/2}}, \quad (6)$$

because $\xi_{ab}^+/\xi_c^+ = \gamma$ and the growth of ξ_{ab}^+ is limited by $\xi_{ab}^+ = L_{H_c} \simeq \sqrt{\Phi_0/(aH_c)}$. On the other hand, in the strict 2D case ξ_c^+ cannot grow beyond the thickness d_s of the system. Consequently, as $-m/H_c$ and ξ_{ab}^+ initially increase with reduced temperature in a fixed field they

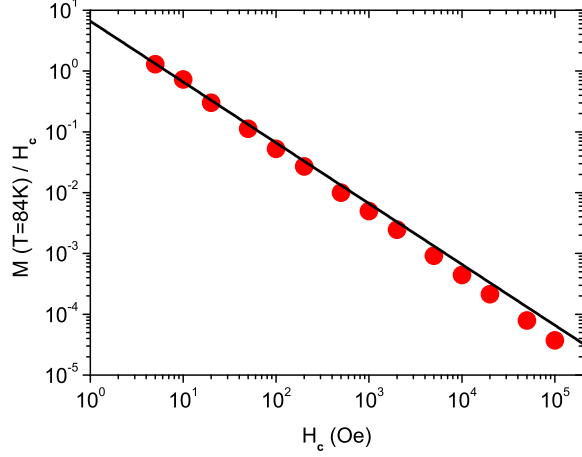


FIG. 3: M/H vs. H for $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ at $T = 84$ K derived from the magnetization data of Li *et al.* [10] with H applied along the c -axis. The solid line is $M(T = 84\text{K})/H = 6.6/H$ corresponding to Eq. (7).

then saturate due to the magnetic field induced finite size effect. In this case Eq. (5) reduces to

$$\frac{m}{H_c} = -\frac{Q^+ C_{3,0}^+ k_B T}{\Phi_0 d_s a H_c}. \quad (7)$$

In Fig. 3 we show $-M/H$ vs. H for $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ close to T_c at $T = 84$ K derived from the magnetization data of Li *et al.* [10], with H applied along the c -axis. The comparison with the characteristic 2D-behavior (7) reveals remarkable agreement, extending over nearly two decades of the applied magnetic field. Noting that down to the lowest applied magnetic field, $H_c = 5$ Oe, there is no sign of leveling off, arising from an inhomogeneity induced finite size effect, it follows that the length of the homogenous regions in the ab -plane, L_{ab} , exceeds the attained magnetic field induced limiting length $L_{H_c} = \sqrt{\Phi_0/(aH_c)} = 1.14 \cdot 10^{-4}$ cm. This behavior does not confirm the occurrence of intermediate 2D critical behavior in sufficiently anisotropic systems above T_c only. In addition, it uncovers that in the ab -plane excellent homogeneity can be achieved and an applied magnetic field leads to the outlined finite size effect.

To substantiate the occurrence of the magnetic field induced finite size effect further, we consider the temperature dependence of the magnetization at fixed magnetic field. When $\xi_c^+ < 3s$ and $L_{H_c} \gg \xi_{ab}^+$ Eq. (5) reduces to

$$\frac{m}{TH_c} = -\frac{Q^+ C_{3,0}^+ k_B (\xi_{ab}^+)^2}{\Phi_0^2 d_s}. \quad (8)$$

In this regime the in-plane correlation length ξ_{ab}^+ is expected to exhibit the characteristic BKT-behavior in

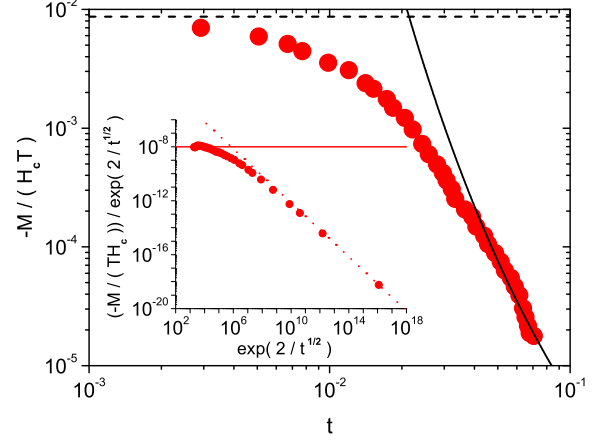


FIG. 4: $-M/(TH_c)$ vs. $t = T/T_c - 1$ for $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$ at $H_c = 10$ Oe with $T_c = 84$ K derived from the magnetization data of Li *et al.* [10]. The solid line is $-M/(TH_c) = 10^{-8} \exp(2/t^{1/2})$ corresponding to Eq. (8) with $\xi_{ab}^+ \propto \exp(bt^{-1/2})$ with $b = 1$ and the dashed one $-M/(TH_c) = 8.7 \cdot 10^{-3}$. The inset shows the finite-size scaling function in terms of $(-M/(TH_c))/\exp(2bt^{-1/2})$ vs. $\exp(2bt^{-1/2})$ with $b = 1$. The dotted line is $(-M/(TH_c))/\exp(2bt^{-1/2}) = 0.007/\exp(2bt^{-1/2})$, indicating the limiting magnetic field induced finite-size behavior and the solid one is $(-M/(TH_c))/\exp(2bt^{-1/2}) = 10^{-8}$ marking the BKT limit.

the reduced temperature $t = T/T_c - 1$, namely $\xi_{ab}^+ = a \exp(bt^{-1/2})$ [2], with $b \approx 1$ a non-universal constant and a related to the vortex core diameter. However, as t decreases and with that ξ_{ab}^+ approaches the limiting length $L_{H_c} = \sqrt{\Phi_0/(aH_c)}$ a finite size effect sets in and ξ_{ab}^+ saturates in the limit $L_{H_c} \ll \xi_{ab}^+$ to $\xi_{ab}^+ = L_{H_c}$. To describe the resulting crossover we introduce the finite-size scaling function S [32] in terms of $(\widetilde{\xi_{ab}^+})^2 = (\xi_{ab}^+)^2 S(H_c (\xi_{ab}^+)^2 / \Phi_0) = (\xi_{ab}^+)^2 S((\xi_{ab}^+)^2 / (aL_{H_c}^2))$ where $S((\xi_{ab}^+)^2 / (aL_{H_c}^2)) \rightarrow 1$ for $L_{H_c} \gg \xi_{ab}^+$, $S((\xi_{ab}^+)^2 / (aL_{H_c}^2)) \rightarrow saL_{H_c}^2 / (\xi_{ab}^+)^2$ for $L_{H_c} \ll \xi_{ab}^+$, and substitute $\widetilde{\xi_{ab}^+}$ in Eq. (8) instead of ξ_{ab}^+ . In Fig. 4 we depicted $-M/(TH_c)$ vs. $t = T/T_c - 1$ at $H_c = 10$ Oe and the inset shows the finite-size scaling function in terms of $(-M/(TH_c))/\exp(2bt^{-1/2})$ vs. $\exp(2bt^{-1/2})$. It is seen that by approaching the transition temperature $-M/(TH_c)$ increases but saturates to $-M/(T_c H_c) = 8.7 \cdot 10^{-3}$, in agreement with the behavior shown in Fig. 3. Sufficiently away from T_c a crossover to the BKT behavior, requiring $L_{H_c} \gg \xi_{ab}^+$ and indicated by the solid line, can be anticipated. As the crossover extends over a rather extended temperature regime agreement with the leading BKT behavior is limited and the 3D-

xy critical regime is not accessible. Nevertheless, the finite-size scaling function reveals the flow to BKT behavior is attained. To provide a consistency test we use $M(T = 84K)/H_c = 6.6/H_c$ (Fig. 3) and $d_s = 15 \text{ \AA}$ to estimate a from $(-M/(TH_c))/\exp(2bt^{-1/2}) = 10^{-8}$ (4) with the aid of Eqs. (7) and (8). The result is $a \simeq 9.2 \text{ \AA}$, in reasonable agreement with the estimate of Li *et al.* [10].

We have seen that the conflicting observations in the highly anisotropic $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$, evidence for BKT behavior emerging from the magnetization data of Li *et al.* [10] and smeared 3D-xy behavior, stemming from the temperature dependence of the magnetic in-plane penetration depth [13, 16, 22] are a consequence of the rather small ratio, $\xi_c^+/\xi_c^- = \xi_{c0}^+/\xi_{c0}^- \simeq 0.45$, between the c -axis correlation length probed above (ξ_c^+) and below (ξ_c^-) T_c and the comparatively large anisotropy. The latter leads to critical amplitudes $\xi_{c0}^\pm$ which are substantially smaller than the distance between two CuO_2 double layers. In combination with $\xi_c^+/\xi_c^- \simeq 0.45$ and in contrast to the situation below T_c the c -axis correlation length ξ_c^+ exceeds the distance between two CuO_2 double layers very close to T_c only. Below this narrow temperature regime where 3D-xy fluctuations dominate, there is then an extended temperature regime left where the units with two CuO_2 double layers are nearly uncoupled so that 2D thermal fluctuations dominate and BKT features are observable. As this behavior relies on the universal ratio $\xi_c^+/\xi_c^- \simeq 0.45$ and pronounced anisotropy it is not an artefact of $\text{Bi}_2\text{Sr}_2\text{CaCu}_2\text{O}_{8+\delta}$, but a generic feature of sufficiently anisotropic cuprate superconductors. Examples include underdoped $\text{La}_{2-x}\text{Sr}_x\text{CuO}_4$ and $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ where the temperature dependence of the in-plane superfluid density does not reveal any trace of the universal jump [13, 14, 15, 16, 17, 18, 19, 20, 21].

[1] V.L. Berezinskii, Zh. Eksp. Teor. Fiz. **61**, 1144 (1971); [Sov. Phys. JETP **34**, 610 (1972)].
 [2] J. M. Kosterlitz and D. J. Thouless, J. Phys. C **6**, 1181 (1973); J. M. Kosterlitz, J. Phys. C **7**, 1046 (1974).
 [3] D. R. Nelson and J. M. Kosterlitz, Phys. Rev. Lett. **39**, 1201 (1977).
 [4] P. Minnhagen, Rev. Mod. Phys. **59**, 1001 (1987).
 [5] T. Schneider and J. M. Singer in *Phase Transition Approach to High Temperature Superconductivity* (Imperial College Press, London, 2000).

[6] T. Schneider, Physica B **326**, 289 (2003).
 [7] S. Vadlamannati, Q. Li, T. Venkatesan, W. L. McLean, and P. Lindenfeld, Phys. Rev. B **44**, 7094 (1991).
 [8] J. Corson *et al.*, Nature (London) **398**, 221 (1999).
 [9] Yayu Wang, Z. A. Xu, T. Kakeshita, S. Uchida, S. Ono, Yoichi Ando, and N. P. Ong, Phys. Rev. B **64**, 224519 (2001).
 [10] Lu Li, Yayu Wang, M. J. Naughton, S. Ono, Yoichi Ando, and N. P. Ong, Europhys. Lett. **72**, 451 (2005).
 [11] Yayu Wang, Lu Li, M. J. Naughton, G. D. Gu, S. Uchida, and N. P. Ong, Phys. Rev. Lett. **95**, 247002 (2005).
 [12] D. Matthey, N. Reyren, and J.-M. Triscone, and T. Schneider, Phys. Rev. Lett. **98**, 057002 (2007).
 [13] T. Jacobs, S. Sridhar, Q. Li, G. D. Gu, and N. Koshizuka, Phys. Rev. Lett. **75**, 4516 (1995).
 [14] C. Panagopoulos, J. R. Cooper, and T. Xiang, Phys. Rev. B **57**, 13422 (1998).
 [15] C. Panagopoulos *et al.*, Phys. Rev. B **60**, 14617 (1999).
 [16] K. D. Osborn, D. J. Van Harlingen, Vivek Aji, N. Goldenfeld, S. Oh, and J. N. Eckstein, Phys. Rev. B **68**, 144516 (2003).
 [17] A. Hosseini, *et al.*, Phys. Rev. Lett. **93**, 107003 (2004).
 [18] D. M. Broun, *et al.*, cond-mat/0509223.
 [19] R. Liang, D. A. Bonn, W. N. Hardy, and D. Broun, Phys. Rev. Lett. **94**, 117001 (2005).
 [20] Y. Zuev *et al.*, Phys. Rev. Lett. **95**, 137002 (2005).
 [21] A. Rüfenacht, J.-P. Locquet, J. Fompeyrine, D. Caimi, and P. Martinoli, Phys. Rev. Lett. **96**, 227002 (2006).
 [22] T. Schneider and D. Di Castro, Phys. Rev. B **69**, 024502 (2004).
 [23] V. G. Kogan, cond-mat/0611187.
 [24] S. Kawamata, K. Inoue, K. Okuda, and T. Sasaki, Physica B **246-247**, 437 (1998).
 [25] T. Watanabe, T. Fujii, and A. Matsuda, Phys. Rev. Lett. **79**, 2113 (1997).
 [26] T. Schneider, in: *The Physics of Superconductors*, edited by K. Bennemann and J. B. Ketterson (Springer, Berlin, (2004)).
 [27] A. Pelissetto and E. Vicari, Physics Reports **368**, 549 (2002).
 [28] T. Schneider, J. Hofer, M. Willemin, J.M. Singer, and H. Keller, Eur. Phys. J. B **3**, 413 (1998).
 [29] J. Hofer, T. Schneider, J. M. Singer, M. Willemin, H. Keller, C. Rossel, and J. Karpinski, Phys. Rev. B **60**, 1332 (1999).
 [30] J. Hofer, T. Schneider, J. M. Singer, M. Willemin, H. Keller, T. Sasagawa, K. Kishio, K. Conder, and J. Karpinski, Rev. B **62**, 631 (2000).
 [31] T. Schneider, Journal of Superconductivity, **17**, 41 (2004).
 [32] *Finite-Size Scaling*, edited by J. L. Cardy (North Holland, Amsterdam, 1988).